

High-purification of amorphous silica originated from rice husks by combination of polysaccharide hydrolysis and metallic impurities removal

Junko Umeda, Katsuyoshi Kondoh*

Joining and Welding Research Institute, Osaka University, 11-1, Mihogaoka, Ibaragi, Osaka 567-0047, Japan

ARTICLE INFO

Article history:

Received 7 May 2010

Received in revised form 1 July 2010

Accepted 4 July 2010

Keywords:

Rice husk

Silica

Hydrolysis

Polysaccharide

Monosaccharide

Metallic impurities

ABSTRACT

Rice husks and straw, containing 70–75 mass% organics and 15–20 mass% amorphous silica (SiO_2), are representative non-eatable biomasses. After the use of the organic elements as fuels, the leavings including large amounts of silica can be used as industrial materials when their purity is 99 mass% or more. Hence, the reuse of high-purity silica will be significantly effective in reducing the total cost of biomass energy in using rice husks and straws. To attain high-purity silica from the remains of the rice husks after air combustion, the optimization of the process conditions of the citric acid leaching treatment and water rinsing process of rice husks were conducted to remove the metallic impurities such as Na, K, Ca, Mg, Fe, Cu, etc. from husks and promote the hydrolysis reaction of polysaccharides. When the citric acid solution with a concentration of 1 mass% or more was used, alkali metal oxides of Na_2O and K_2O were completely removed. GC–MS analysis showed the progress of the hydrolysis reaction of their hemi-cellulose of rice husks during the leaching process. Carbon content of ashes was drastically reduced to 0.02–0.04 mass% after combustion at 1073–1273 K, and high-purity amorphous silica with 99.5–99.77 mass% were produced from rice husks.

© 2010 Elsevier B.V. All rights reserved.

1. Introduction

Rice husks and straws are representative agricultural wastes in the world. The annual yield of rice husks was about 127 million tons in 2008 (FAO, 2008). At this moment, most of them are not practically reused, and cause the environmental problems. For example, the combustion of 1 ton rice husks in the field causes about 0.15 kg CO_2 gas emission. Approximate 0.09 kg methane (CH_4) gas is produced when 1 ton rice husks are left on the ground and naturally decomposed (Klass, 1998). From a viewpoint of the reuse of rice husks and straws as fuel resources, they are useful biomass materials. This is because they contain about 65–75 mass% polysaccharide organics such as cellulose and hemi-cellulose (Aristidou and Penttilä, 2000) and become suitable fuel resources for energy generation (Jain et al., 1994; Fang et al., 2004). On the other hand, amorphous silica materials of about 12–20 mass% are contained in rice husks and straws (Aristidou and Penttilä, 2000; Yalçın and Sevinç, 2001), and certainly remain in their leavings after using the organic elements as fuels. In general, silica is useful industrial materials such as fertilizer, reinforcement of concretes, and ceramics materials (Della et al., 2002; Sensale, 2006; Krishnarao and Godkhindi, 1992). A lot of previous studies have suggested some

processes to produce silica materials by combusting rice husks (Chakraverti et al., 1988; Kalapathy et al., 2000; Patel et al., 1987; Rozainee et al., 2008). From a high-purification of silica originated in rice husks, a strong acid solution washing process was used to remove the alkali metal impurities (Na and K) from the husks (Liou and Wu, 2009; Chakraverti et al., 1988; Rhaman et al., 1997). This is because metal impurities of Na and K elements have a eutectic reaction with SiO_2 during combustion of rice husks (Allendorf and Spear, 2001; Besmann and Spear, 2002). For example, when Na_2O and SiO_2 coexists in rice husks, the ternary oxides, $\text{Na}_6\text{Si}_8\text{O}_{19}$ and $\text{Na}_2\text{Si}_2\text{O}_5$ with a eutectic melting point of 1062 K (Morey et al., 1930; Richet et al., 2006) are formed during combustion in air, and results in a drastic decrease of the melting point of SiO_2 from 1986 to 1062 K occurs (Yazhenskikh et al., 2006; Haltera and Mysen, 2004). Therefore, the carbon elements originated from organics of rice husks easily dissolve and remain in such ternary Si–Na–O and Si–K–O oxides in liquid phase during combustion at 1073–1273 K. As a result, the purity of silica materials contained in the rice husk leavings was 96–98 mass% or less. Furthermore, a large part of amorphous silica changes to crystalline structures after solidification of the above ternary oxides. The authors have established an environmentally benign process to produce rice husk silica with a high-purity of 99 mass% and over by using the citric acid solution leaching treatment before combustion (Umeda et al., 2007; Umeda and Kondoh, 2008). Such silica materials also showed completely amorphous structures even after combustion at 1273 K in

* Corresponding author.

E-mail address: kondoh@jwri.osaka-u.ac.jp (K. Kondoh).

air because the metal impurities were removed from husks during the above acid leaching treatment. The use of the citric acid solution is effective for the chelate reaction (Norman and Earnshaw, 1997) between carboxyl groups ($-\text{COOH}$) and metallic impurities contained in husks, and results in the removal of such impurities as metal complexes from rice husks during the leaching treatment. In the present study, from a view point of a higher purification of amorphous silica, the optimization of the process parameters in the acid leaching treatment and combustion of rice husks was discussed. In particular, the effect of the citric acid concentration on the polysaccharide hydrolysis behavior of organics was investigated by using GC–MS analysis, and the removal mechanism of metallic impurities was also discussed.

2. Experimental

Rice husks harvested in Niigata were used as input raw materials to produce high-purity amorphous silica materials. As mentioned above, the previous study clarifies that the citric acid solution leaching treatment and air combustion of rice husks are useful for the removal of the metallic impurities (Umeda et al., 2007; Umeda and Kondoh, 2008). Citric acid powders, having a mean particle size of 1.22 mm, were dissolved in the distilled water at the ambient temperature to prepare citric acid solutions. 30 g rice husks were put into 500 ml citric acid solution in Griffin beaker. In the present study, the concentration and temperature of the citric acid solution, and stirring time in the solution were selected as the operating parameters. This is because the chelate reaction between $-\text{COOH}$ groups and metallic impurities strongly depends on the above parameters and the hydrolysis of polysaccharides of cellulose and hemi-cellulose is also dependent on them. The concentration was controlled from 1 to 7 mass% by changing the mixing ratio of citric acid powders (Kishida Chemical Co., purity; 99.5 mass%) and distilled water. The beaker was placed on the stirrer (AS ONE, hot stirrer, HS-5BHSD), and the solution temperature was changed from 298 to 353 K. The rotating speed of the magnetic stirrer bar in the solution was controlled at 960 rpm, and the stirring time was 15–120 min. After the acid leaching process, the water rinsing treatment of the rice husks was carried out in the distilled water at 293 K for 900 s to remove the citric acid content from the husks. The stirrer was also used in the water rinsing process, and the magnetic bar was rotated under 960 rpm speed. The materials were dried at 373 K for 60 min in the muffle furnace in atmosphere, and then combusted at 1073 K for 30 min in the same furnace. The combustion temperature of 1073 K was used in this study to prevent the crystallization of amorphous silica contained in the husks (Rhaman et al., 1997). The airflow rate in the combustion was 0.42 ml/s by using a small air-compressor. The content of each metallic oxide impurity of the ashes was measured by X-ray fluorescence spectroscopy (XRF, PANalytical, X-ray spectrometer PW2400). Carbon analyzer (HORIBA, EMIA-902V) was employed to measure the carbon content of the ashes. Fourier transform-infrared spectrometer (FT-IR, Nicolet, MagnaIR-560 with Dura-ATR, Sens-IR) analysis was also carried out to investigate structures of the remained carbides originated from the organic elements and silica materials. In order to quantitatively evaluate the hydrolysis behavior of the polysaccharides of rice husks by using the citric acid leaching treatment, gas chromatograph–mass spectrometer (GC–MS, Agilent Technologies, Agilent-5973N) was applied to the acid-leached specimens after air dry at 373 K. As mentioned in the previous report (Umeda and Kondoh, 2008), the same heat treatment of them was conducted at 473 K for 360 s before GC–MS analysis. The hydrolysis behavior of the organics was investigated by comparing the identification of the mass spectra and their intensities, and the effect of the citric acid concentration on the polysaccharide hydrolysis was discussed.

Table 1

Quantitative analysis of silica (SiO_2) and impurities contents of rice husk ashes by using citric acid leaching treatment with various concentrations (leaching temperature; 323 K, soaking time; 60 min, water rinsing time; 15 min, air-burning conditions; 1073 K \times 30 min).

Mass%	Concentration of citric acid solution (wt.%)				
	0%	1%	3%	5%	7%
SiO_2	97.25	99.52	99.54	99.56	99.47
MgO	0.29	0.04	0.03	0.02	0.03
Na_2O	0.13	0.00	0.00	0.00	0.00
P_2O_5	0.09	0.11	0.12	0.13	0.13
S	0.03	0.02	0.02	0.02	0.01
K_2O	1.39	0.03	0.02	0.01	0.02
CaO	0.46	0.16	0.13	0.11	0.12
Cr_2O_3	0.00	0.00	0.01	0.00	0.04
MnO	0.13	0.02	0.02	0.01	0.02
Fe_2O_3	0.02	0.02	0.05	0.02	0.04
NiO	0.00	0.00	0.00	0.00	0.02
CuO	0.00	0.00	0.00	0.00	0.00
MoO_3	0.00	0.00	0.00	0.00	0.00
C	0.15	0.08	0.06	0.04	0.03

3. Results and discussion

3.1. Effect of citric acid solution leaching and water rinsing conditions on removal of metallic impurities

Table 1 shows chemical compositions of the rice husk ashes via the citric acid solution leaching treatment with different concentration. The solution temperature was 323 K and the stirring time of 60 min was used in the leaching process. The concentration of 0 mass% means the use of the warm distilled water rinsing treatment at 323 K instead of the citric acid solution. As shown in Table 1, when the concentration of the citric acid solution is over 1 mass%, the silica (SiO_2) purity of each ash is approximately 99.5 mass% or more. On the other hand, a silica purity of 97.25 mass% was obtained by using the warm distilled water leached treatment (0 mass%). It means the use of the citric acid leaching treatment obviously caused the remarkable reduction of the total content of metal oxide impurities, and resulted in a high-purification of silica materials contained in the rice husk ashes. Concerning the content of alkali metal oxides (Na_2O and K_2O) remained in the ashes, the application of the citric acid solution is remarkably effective in reducing them. In particular, Na_2O has been completely removed from the rice husks by using the citric acid solution of 1 mass% or more concentration. When the warm distilled water (0 mass%) was employed, the content of K_2O and carbon remained in the ashes was 1.39 and 0.15 mass%, respectively. The previous result indicates that K_2O and carbon content of rice husk ashes was 3.69 and 0.61 mass%, respectively when raw rice husks with no leaching treatment were used (Umeda and Kondoh, 2008). This means that even the warm distilled water leaching treatment is effective for the removal or reduction of K impurities from rice husks. This is because the hydrolysis reaction of polysaccharides such as cellulose and hemi-cellulose occurred during leaching treatment by using warm distilled water at 323 K for 60 min, and the chelate between K impurities and $-\text{COOH}$ groups easily took place. The reason for the reduction of carbon content is due to the removal of K_2O impurities, causing a eutectic reaction of SiO_2 elements at lower temperature and their liquid phase. The content of MgO and MnO impurities remained in the ashes is also extremely reduced by using the citric acid solution, and their reduction ratio is 85–93% when comparing to the oxide impurities of the ashes via the warm distilled water leaching treatment (0 mass%). Furthermore, it is obvious that the citric acid solution leaching treatment is also effective in removing Ca elements from rice husks. However, its reduction ratio of about 65–76% is smaller than those of MgO and MnO as men-

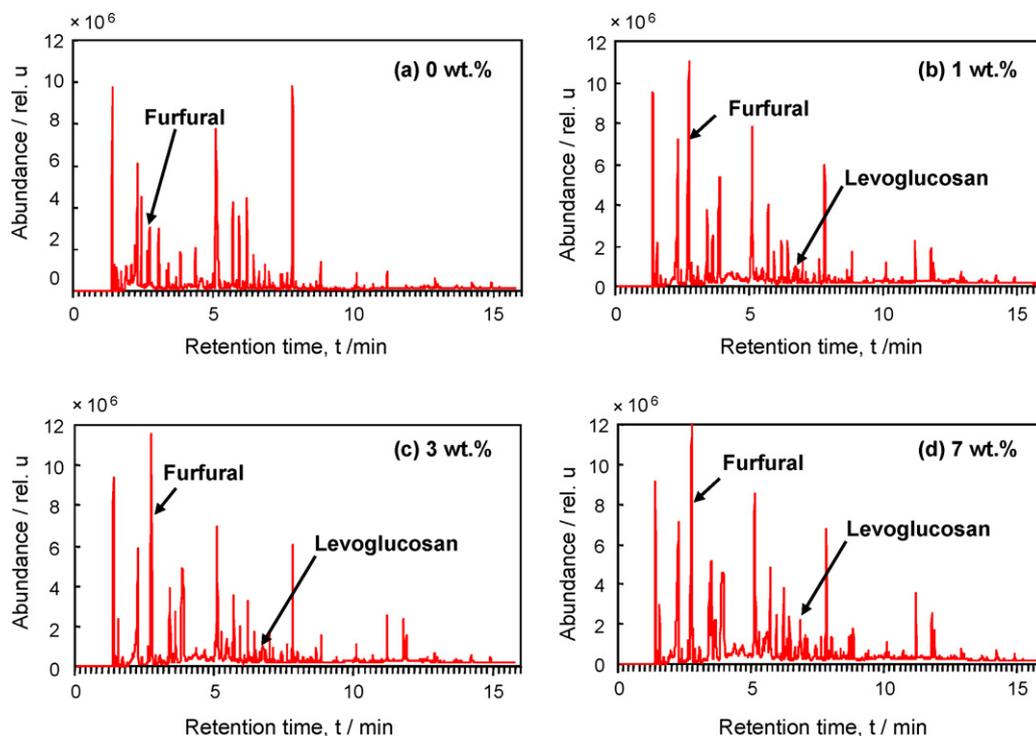


Fig. 1. GC-MS analysis results of rice husks via citric acid solution leaching treatment using various solution concentrations of 0 mass% (a), 3 mass% (b), 5 mass% (c), and 7 mass% (d) (solution temperature; 323 K, pre-heating condition; 473 K for 6 min).

tioned above. Fig. 1 indicates GC-MS analysis results of air-dried rice husks via the citric acid leaching and the next water rinsing treatment. The concentration of the citric acid solution used in this analysis is 0 mass% (a), 1 mass% (b), 3 mass% (c) and 7 mass% (d). The spectrum corresponding to furfural, which is a monosaccharide formed from hemi-cellulose via hydrolysis and dehydration reaction (Saha, 2003), is clearly detected in specimens of the citric acid-leached husks (b)–(d). As shown in (a), a small peak of furfural is also detected. It means the warm water leaching treatment at 323 K is also slightly effective in the hydrolysis and dehydration reaction of hemi-cellulose. It also reveals no obvious difference of the spectrum intensity between 1 and 7 mass% concentration. A very small spectrum of levoglucosan is detected in all materials shown in Fig. 1. Fig. 2 shows a dependence of the ion intensity of the furfural spectrum on the concentration of the citric acid solution. When 1 mass% citric acid solution is used, the ion intensity

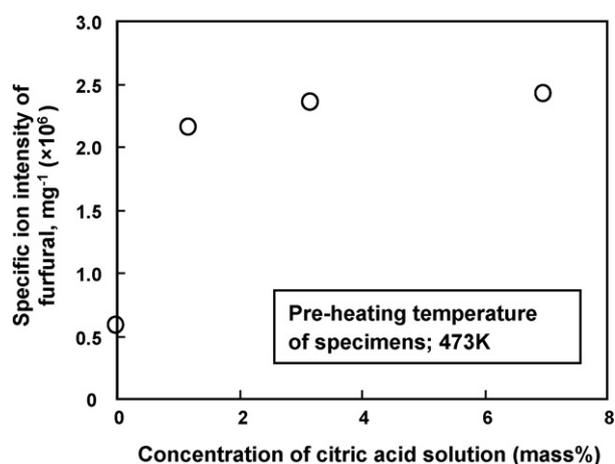


Fig. 2. Specific ion intensity of furfural spectrum in GC-MS results of rice husks via citric acid leaching treatment as a function of acid solution concentration.

is 2.21×10^6 (mg^{-1}) and about four times as that in the use of the warm distilled water shown in Fig. 1(a). It slightly increases with increasing concentration from 1 to 7 mass%. These results suggest that the citric acid solution of 1 mass% concentration is enough for the progress of hydrolysis reaction of hemi-cellulose (polysaccharide) to furfural (monosaccharide) contained in rice husks. The previous study shows that the metallic impurities such as Na, K, Ca, Mg, Fe, Al and Mn are contained in the rice husk organics consisting of hemi-cellulose and cellulose (Horng, 2004). When the hydrolysis reaction of the polysaccharides progresses by the citric acid leaching treatment, the simple structures of monosaccharides such as furfural and levoglucosan are formed in the rice husks (Saha, 2003). As a result of this reaction, carboxyl groups easily pass through the monosaccharides and contact the above metallic impurities contained in rice husks. Their chelate complexes are formed and discharged from the husks into the acid solution. Therefore, as shown in Table 1, the content of each metallic impurity oxide of the ashes are drastically reduced by the citric acid solution leaching treatment. In addition, Table 1 obviously indicates that the reduction of alkali metal oxides of Na_2O and K_2O is effective to decrease the remained carbon content of the ashes. This is because a remarkable decrease of these oxide impurities, causing a liquid phase of SiO_2 by the eutectic reaction at 1062 K as mentioned above, prevents the dissolution of carbon elements in the melt SiO_2 during combustion at 1073 K. Hence, a very few organics remain in the ashes, and result in a high-purification of silica materials.

Table 2 shows chemical compositions of the rice husk ashes when the citric acid solution with different temperature was used in the leaching treatment. The solution concentration and stirring time were 5 mass% and 60 min, respectively. The result in Table 1 indicates that the concentration of 1 mass% is enough for the removal of metallic impurities from the rice husks when the citric acid solution leaching is applied. However, Fig. 2 also suggests that a slight increase of the furfural spectrum intensity with increase in the solution concentration. Accordingly, 5 mass% concentration of the citric acid solution is applied to evaluate the effect of the

Table 2

Quantitative analysis of silica (SiO_2) and impurities contents of rice husk ashes by using citric acid leaching treatment at various temperatures (citric acid solution concentration; 5 mass%, soaking time; 60 min, water rinsing time; 15 min, air combustion conditions; $1073 \text{ K} \times 30 \text{ min}$).

Mass%	Citric acid solution temperature				
	298 K	313 K	323 K	333 K	353 K
SiO_2	99.25	99.54	99.56	99.58	99.77
MgO	0.07	0.05	0.02	0.09	0.04
Na_2O	0.00	0.00	0.00	0.00	0.00
P_2O_5	0.13	0.12	0.13	0.12	0.10
S	0.02	0.02	0.02	0.00	0.00
K_2O	0.08	0.02	0.01	0.02	0.00
CaO	0.27	0.14	0.11	0.08	0.03
Cr_2O_3	0.00	0.00	0.00	0.00	0.00
MnO	0.05	0.02	0.01	0.01	0.00
Fe_2O_3	0.03	0.02	0.02	0.02	0.02
NiO	0.00	0.00	0.00	0.00	0.00
CuO	0.02	0.00	0.00	0.00	0.00
MoOg	0.00	0.04	0.00	0.00	0.00
C	0.05	0.06	0.04	0.02	0.03

solution temperature on the removal of metallic impurities. With increase in the temperature, most of the impurities are removed, and a purity of the silica is gradually improved. In particular, it reaches 99.77 mass% by using the citric acid solution of 353 K. In the case of Na_2O , even the acid leaching treatment at 298 K is enough to remove Na impurities from rice husks. On the other hand, CaO content of the ashes gradually decreases with increasing the solution temperature. It means that higher temperature of the acid solution is more effective in removing Ca impurity from the rice husks. Fig. 3(a) indicates the Ca content of the used citric acid solution after the leaching treatment as a function of the solution temperature. The CaO content of the ashes shown in Fig. 3(b) is originated from Table 2. Ca elements are discharged into the acid solution during acid leaching process, and their content of the solution gradually increases with increasing the temperature. By using these measurements, a ratio of the content of Ca impurities discharged from rice husks to the original Ca content is estimated. In this calculation, it

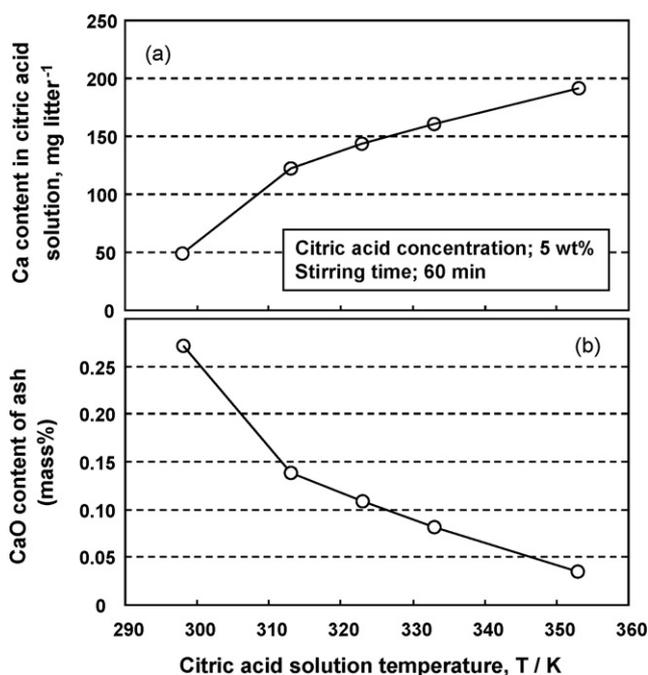


Fig. 3. Ca content in citric acid solution (a) and CaO content of ash (b) dependence on citric acid solution temperature (citric acid solution concentration; 5 mass%, stirring time; 60 min, air combustion temperature; 1073 K).

Table 3

Dependence of discharged rate of Ca from rice husks into citric acid solution on solution temperature (concentration of citric acid solution; 5 mass%, stirring time; 60 min).

Temperature, T (K)	298	313	323	333	353
Discharged ratio (%)	34.0	72.0	78.9	85.3	94.5

is assumed that Ca is removed by only the acid leaching treatment, not the next water rinsing process. Hence, the original Ca content of rice husks is the sum of that of the ashes and the used citric acid solution. As shown in Table 3, the ratio of Ca impurities discharged into the acid solution is 34% by using the ambient temperature acid leaching treatment (298 K). However, it suddenly increases to 72% when the warm acid solution of 313 K is employed. With increase in the solution temperature, the ratio gradually increases, and reaches 94.5% at 353 K. From a viewpoint of a chemical reaction, a higher temperature of the citric acid solution is effective for both formation of Ca complexes by the chelate and hydrolysis reaction from polysaccharides to monosaccharides, and results in the progress of a discharge of the complexes from rice husks.

Fig. 4 indicates the effects of the stirring time during the citric acid leaching and the next water rinsing treatment on the CaO content of the rice husk ashes. The concentration and temperature of the citric acid solution were 5 mass% and 323 K, respectively. The stirring time in the acid leaching and water rinsing treatment are obviously useful to reduce the CaO impurity content. In particular, the citric acid leaching time is much dominant on the reduction of CaO elements. According to the above results shown in Tables 1, 2 and Fig. 1, it is concluded that not only the removal of metal impurities by the chelate reaction, but also the hydrolysis reaction of polysaccharides by the acid leaching treatment dominate largely a purification of SiO_2 elements of the rice husk ashes.

3.2. Effect of combustion temperature on silica crystal structure and carbon content

The previous studies have mentioned the effect of the combustion temperature on the crystallization behavior of silica materials contained in rice husk ashes (Ibrahim and Helmy, 1981; Shinohara and Kohyama, 2004). In general, the combustion temperature of rice husks at 973 K or more causes the crystallization of amorphous SiO_2 of the ashes when raw rice husks with no acid leaching treatment are used as starting materials. However, as shown in

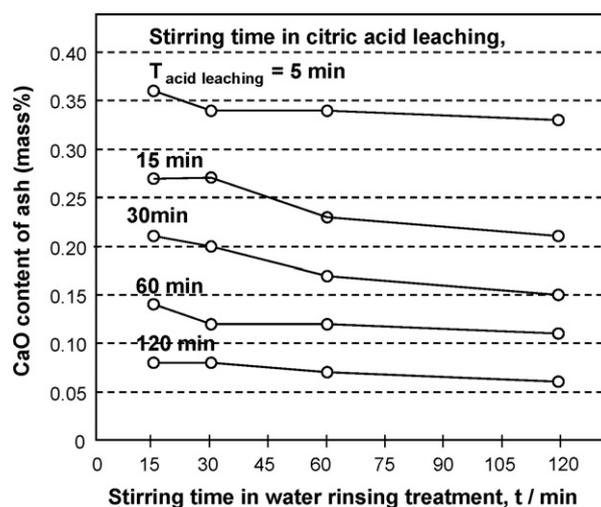


Fig. 4. CaO content of rice husk ashes via citric acid leaching with various stirring time as a function of water rinsing time (citric acid solution; 5 mass% and 323 K, water rinsing at 298 K, air combustion conditions; $1073 \text{ K} \times 30 \text{ min}$).

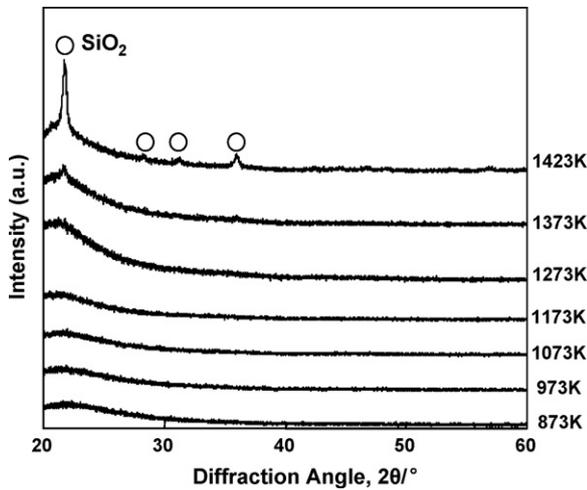


Fig. 5. XRD profiles of rice husk ashes after air combustion at various temperatures (concentration and temperature of citric acid solution leaching treatment are 5 mass% and 323 K, respectively).

Fig. 5, the crystallization temperature of amorphous silica drastically increases from 973 to 1323 K when the citric acid leaching process is applied to rice husks before combustion. This is because a eutectic phenomenon of SiO₂ via reaction with Na₂O or K₂O impurities is prevented by reducing the content of these alkali metal impurities from the rice husks as mentioned above. However, the heating time in the combustion is not significantly effective on the crystallization of amorphous silica originated in rice husks. This is because the crystallization phenomenon drastically occurs when the materials temperature reaches the critical level in combustion (Shinohara and Kohyama, 2004). Therefore, the heating time

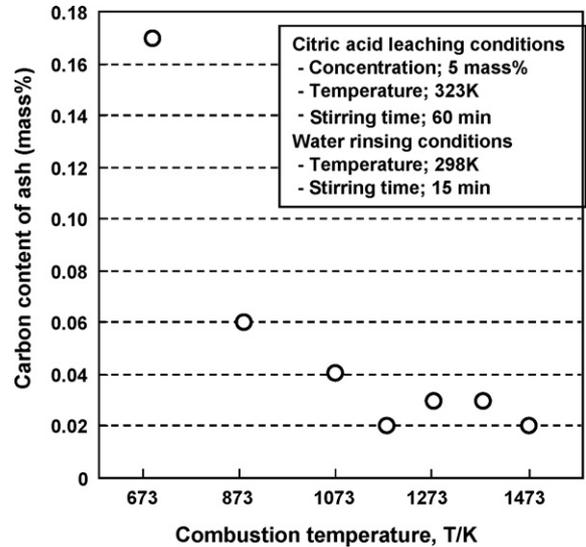


Fig. 6. Dependence of carbon content of rice husk ashes on combustion temperature (citric acid solution concentration; 5 mass%, temperature; 323 K and stirring time; 60 min).

of 1.8 ks used in this study is enough to obtain the stable state of silica materials after combustion in air.

At the same time, the combustion temperature also affects the remained carbon content of their ashes. Fig. 6 shows a dependence of the carbon content of the ashes on the combustion temperature. The content was measured by ICP analysis. 5 mass% citric acid solution was used, and the stirring temperature and time during the acid leaching treatment were 323 K and 60 min, respectively. It is obvious that the remained carbon content remarkably decreases

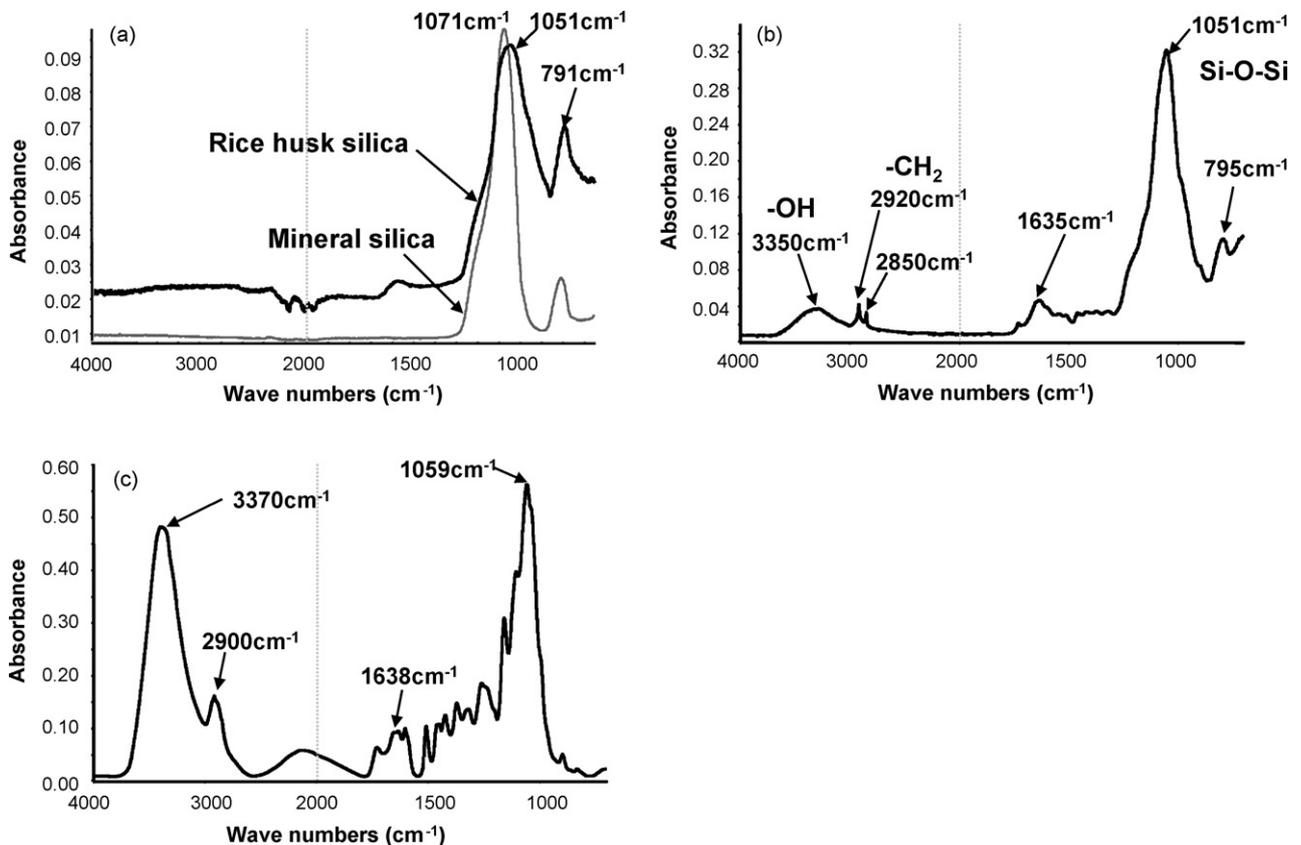


Fig. 7. FT-IR spectra of rice husk ash burned at 1073 K (a) and 673 K (b), compared to commercialized mineral silica particle and raw materials (c).

from 0.17 mass% to 0.02–0.03 mass% by changing the combustion temperature from 673 to 1073 K. In addition, there is no significant difference of the carbon content by burning the husks over 1073 K. DTA profiles of rice husks in the previous study indicate the exothermic heat due to a combustion of the organics was completely finished at 973 K when the husks via the citric acid leaching treatment was used (Umeda and Kondoh, 2008). It means that pyrolysis of the organics contained in rice husks progresses completely by combustion in air over 973 K. Fig. 7 shows the results of FT-IR analysis of rice husk ashes combusted at 1073 K (a) and 673 K (b). The infrared spectrum of the commercial mineral silica powders and raw rice husks is also shown in (a) and (c), respectively. The infrared spectra at 1051 and 791 cm^{-1} due to Si–O–Si stretching modes (Ayres et al., 2007) are detected in (a), and correspond to those of the conventional mineral silica used as reference materials. No spectrum of about 3370–2850 cm^{-1} of the polysaccharides (Ayres et al., 2007; Wang and Sung, 2002) of raw rice husks is obviously observed. It means that a very few carbons originated from the cellulose and hemi-cellulose exist in the ashes after combustion at 1073 K. This result corresponds well to the carbon measurement by ICP analysis shown in Fig. 6. On the other hand, the specimen burned at 673 K shown in Fig. 7(b) indicates not only 1051 and 791 cm^{-1} spectra (Si–O–Si bond) but also small spectra at 3350, 2920 and 2850 cm^{-1} corresponding to OH stretching mode and CH_2 stretch vibrations (Wang and Sung, 2002), which are also detected in the raw rice husks (c). This means that some of original organics still exist in the ashes after combustion at 673 K, and result in the remarkably large content of the remained carbon elements of ashes burned at 673 K as shown in Fig. 6. Therefore, the combustion temperature of 1073–1273 K is suitable for the preparation of high-purity amorphous silica materials originated from rice husks via the citric acid leaching treatment.

4. Conclusion

For a high-purification of amorphous silica originated in rice husks, the optimization of the operating parameters in the citric acid leaching treatment and air combustion of rice husks was discussed. When the citric acid solution with a concentration of 1 mass% or more was used, XRF analysis indicated that the metal oxide impurities could be obviously reduced from rice husks during the acid leaching treatment. In particular, the alkali metal oxides of Na_2O and K_2O were completely removed. GC–MS analysis showed the progress of the hydrolysis reaction of their hemi-cellulose of rice husks during the leaching process. As a result, the carbon content of the ashes was drastically reduced to 0.02–0.04 mass% after combustion at 1073–1273 K. The capability to remove Ca impurities from rice husks by the citric acid leaching treatment was dependent on not only the concentration of the acid solution but also the solution temperature and stirring time. The combustion temperature at 1073 K or more was enough to thermally resolve the original carbohydrates of rice husks, and resulted in a very few carbon contents of 0.02–0.03 mass%. On the other hand, when the combustion temperature of 673 K was employed, FT-IR analysis showed CH_2 and OH stretching modes with 3350–2850 cm^{-1} spectra originated in the carbohydrates of the rice husks. Their ashes including 0.17 mass% carbons were obtained. In the use of the suitable conditions of the acid leaching and air combusting processes, high-purity amorphous silica materials with 99.5–99.77 mass% were produced from rice husks.

Acknowledgement

This study was financially supported in part by “The Japan Securities Scholarship Foundation” in 2008.

References

- Allendorf, M.D., Spear, K.E., 2001. Thermodynamic analysis of silica refractory corrosion in glass-melting furnaces. *J. Electrochem. Soc.* 148, B59–B67.
- Aristidou, A., Penttilä, M., 2000. Metabolic engineering applications to renewable resource utilization. *Biochem. Eng.* 11, 187–198.
- Ayres, E., Vasconcelos, W.L., Oréñice, R.L., 2007. Attachment of inorganic moieties onto aliphatic polyurethanes. *Mater. Res.* 10, doi:10.1590/S1516-14392007000200005, ISSN 1516-1439.
- Besmann, T.M., Spear, K.E., 2002. Thermodynamic modelling of oxide glasses. *J. Am. Ceram. Soc.* 85, 2887–2894.
- Chakraverti, A., Mishra, P., Banerjee, H.D., 1988. Investigation of combustion of raw and acid-leached rice husk for production of pure amorphous white silica. *J. Mater. Sci.* 23, 21–24.
- Della, V.P., Kühn, I., Hotza, D., 2002. Rice husk ash as an alternate source for active silica production. *Mater. Lett.* 57, 818–821.
- Fang, M., Yang, L., Chen, G., Shi, Z., Luo, Z., Cen, K., 2004. Experimental study on rice husk combustion in a circulating fluidized bed. *Fuel Process. Technol.* 85, 1273–1282.
- FAO (Food and Agriculture Organization of the United Nations), 2008. The State of Food and Agriculture in Asia and the Pacific Region. Regional Office for Asia and the Pacific.
- Haltera, W.E., Mysen, B.O., 2004. Melt speciation in the system Na_2O – SiO_2 . *Chem. Geol.* 213, 115–123.
- Horng, L.T., 2004. Preparation and Characterization of Nano-Structured Silica from Rice Husk. *Mater. Sci. Eng. A364*, 313–323.
- Ibrahim, D.M., Helmy, M., 1981. Crystallite growth of rice husk ash silica. *Thermochim. Acta* 45, 79–85.
- Jain, A., Rao, T.R., Sambi, S.S., Grover, P.D., 1994. Energy and chemicals from rice husk. *Biomass Bioenergy* 7, 285–289.
- Kalpathy, U., Proctor, A., Shultz, J., 2000. A simple method for production of pure silica from rice hull ash. *Bioresour. Technol.* 73, 257–262.
- Klass, D.L., 1998. Biomass for Renewable Energy, Fuels, and Chemicals. Academic Press.
- Krishnarao, R.V., Godkhindi, M.M., 1992. Distribution of silica in rice husks and its effect on the formation of silicon carbide. *Ceram. Int.* 18, 243–249.
- Liou, T.H., Wu, S.J., 2009. Characteristics of microporous/mesoporous carbons prepared from rice husk under base- and acid-treated conditions. *J. Hazard. Mater.* 171, 693–703.
- Morey, G.W., Kracek, F.C., Bowen, N.L., 1930. The ternary system K_2O – CaO – SiO_2 . *J. Soc. Glass Technol.* 14, 149–187.
- Norman, N., Earnshaw, A., 1997. Chemistry of the Elements, 2nd ed. Butterworth-Heinemann, Oxford.
- Patel, M., Karera, A., Prasanna, P., 1987. Effect of thermal and chemical treatments on carbon and silica contents in rice husk. *J. Mater. Sci.* 22, 2457–2464.
- Rhaman, I.A., Ismail, J., Osman, H., 1997. Effect of nitric acid digestion on organic materials and silica in rice husk. *J. Mater. Chem.* 7, 1505–1510.
- Richet, P., Roskosz, M., Roux, J., 2006. Glass formation in silicates: insights from composition. *Chem. Geol.* 225, 388–401.
- Rozainee, M., Ngo, S.P., Salema, A.A., Tan, K.G., Ariffin, M., Zainura, Z.N., 2008. Effect of fluidising velocity on the combustion of rice husk in a bench-scale fluidised bed combustor for the production of amorphous rice husk ash. *Bioresour. Technol.* 99, 703–713.
- Saha, B.C., 2003. Hemicellulose bioconversion. *J. Ind. Microbiol.* 30, 279–291.
- Sensale, G.R., 2006. Strength development of concrete with rice-husk ash. *Cem. Concr. Compos.* 28, 158–160.
- Shinohara, Y., Kohyama, N., 2004. Quantitative analysis of tridymite and cristobalite crystallized in rice husk ash by heating. *Ind. Health* 42, 277–285.
- Umeda, J., Kondoh, K., Michiura, Y., 2007. Process parameters optimization in preparing high-purity amorphous silica originated from rice husks. *Mater. Trans.* 48, 3095–3100.
- Umeda, J., Kondoh, K., 2008. High-purity amorphous silica originated in rice husks via carboxylic acid leaching process. *J. Mater. Sci.* 43, 7084–7090.
- Wang, S., Sung, C., 2002. Fluorescence and IR characterization of cure in polyurea, polyurethane, and polyurethane-urea. *Macromolecules* 35, 883–888.
- Yalçın, N., Sevinç, V., 2001. Studies on silica obtained from rice husk. *Ceram. Int.* 27, 219–224.
- Yazhenskikh, E., Hack, K., Muller, M., 2006. Critical thermodynamic evaluation of oxide systems relevant to fuel ashes and slags. Part 1: Alkali oxide–silica systems. *Comput. Coupling Phase Diagrams Thermochem.* 30, 270–276.